

# Evaluation of Performance Properties of Asphalt Mixes Containing RAP Produced with Vacuum Tower Asphalt Extender (VTAE) Modified Binder




John D'Angelo, D'Angelo Consulting LLC  
Ken Grzybowski, Christine Feaster PRI  
Steve Lewis, Mark Bouldin, Safety-Kleen

# The Refinery



# The Refining Process

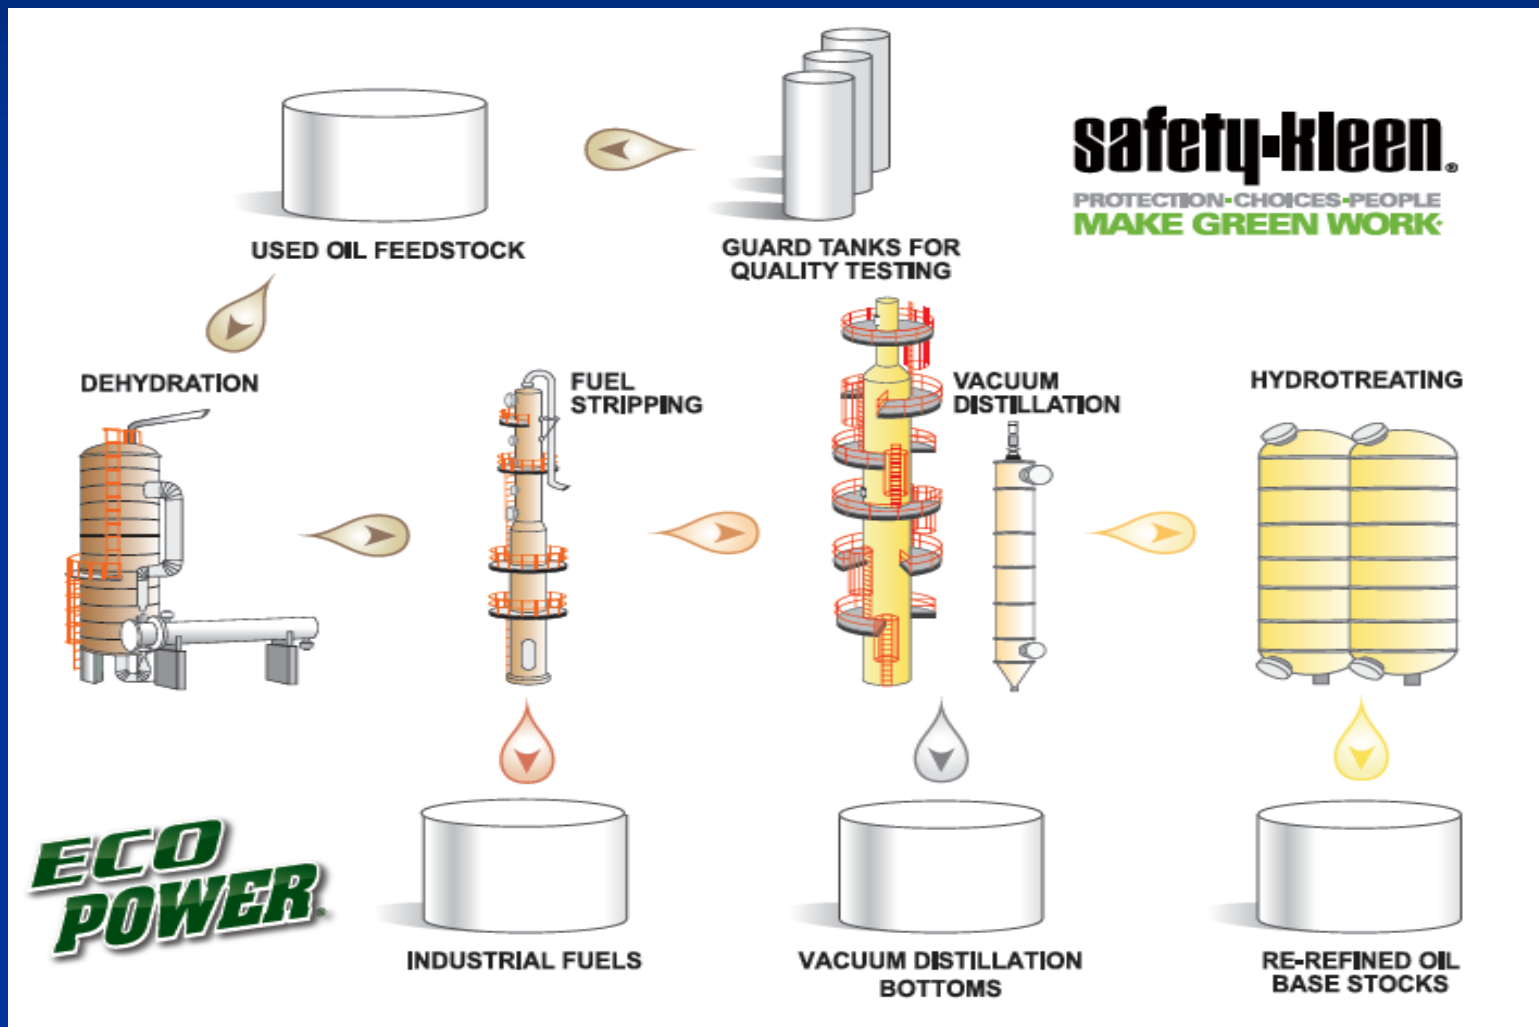

# Re-refined Product



# Results from Previous Studies


- VTAE has been shown effective in reducing high and low temperature properties of a binder.
- Mixes produced with VTAE modified binder have shown improved fatigue and low temperature fracture properties.

# Component makeup of VTAE's

<u>Property</u>		<u>Test Method</u>	<u>Results</u>	
			VTAE 1	VTAE 2
Basic Composition: As Received				
Ash, %		AASHTO T 111	5.7	8.8
Component Fractions, %	Asphaltenes	ASTM D 4124, SARA Fractions by Iatroscan	2.6	6.6
	Polar Aromatics		44.7	51.9
	Naphthene Aromatics		0	0
	Saturates		52.7	41.5
Wax, %		EN 12606-1	0.28	0.1
Solubility, %		ASTM D 2042	99.3	98.7



# VTAE affect on Intermediate DSR Marathon & VTAE 1

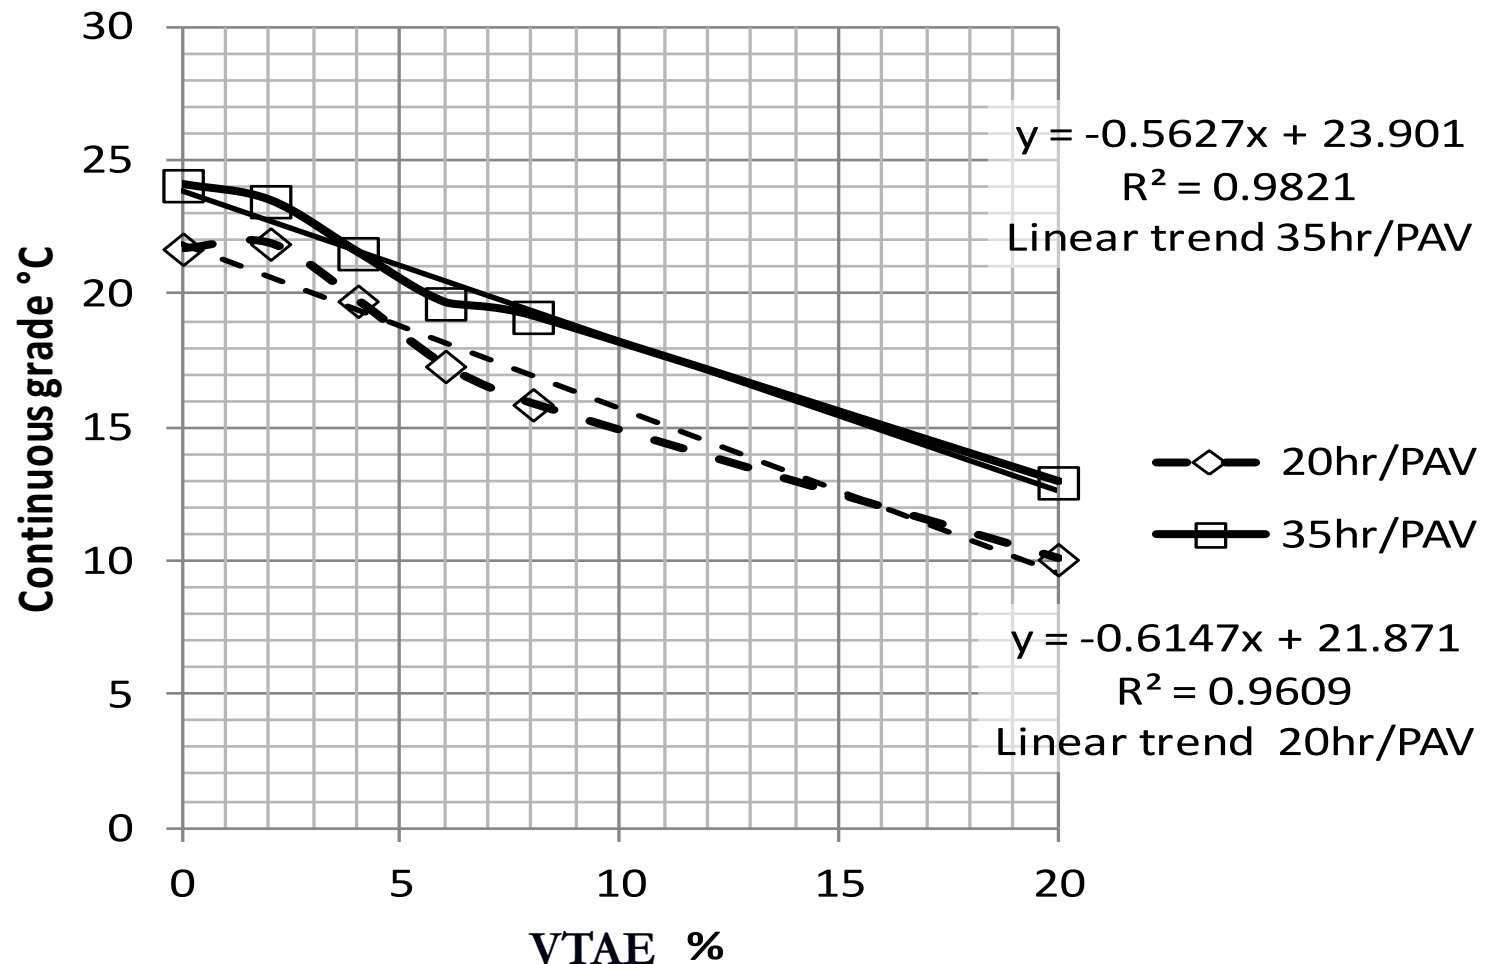

# VTAE affect on Intermediate DSR properties

- VTAE reduced the Intermediate DSR values.
- Linear relationship between % VTAE and reduction.
- Rate of aging is controlled by the base asphalt.
- VTAE does not increase aging.



# Can EcoAddz be used as a Rejuvenator for RAP Mixes

- How will the EcoAddz Affect RAP Mix Properties?
- How will EcoAddz Affect Aging of RAP Mixes?


# Mix Testing of EcoAddz Modified Material with RAP

- Use mix from U. Illinois Moisture damage study N70, 70 gyration Mix
- Use Illinois stone, Dolomitic Limestone
- RAP Local Florida Mix Tampa
  - Recovered binder PG 92.1-14.3
- Control binder BP PG 64-22
- Modify BP PG 64-22 with 2, 6 & 10 % EcoAddz

# Mix Testing of VTAE Modified Material

- High temperature testing Hamburg Wheel tracking
- Intermediate temperature testing 4 Point Bending Beam
- Dynamic Modulus testing
- Low temperature testing Disk Shape Compact Tension
- Short term and long term aging of mix


# Accelerated Pavement Weathering System (APWS)

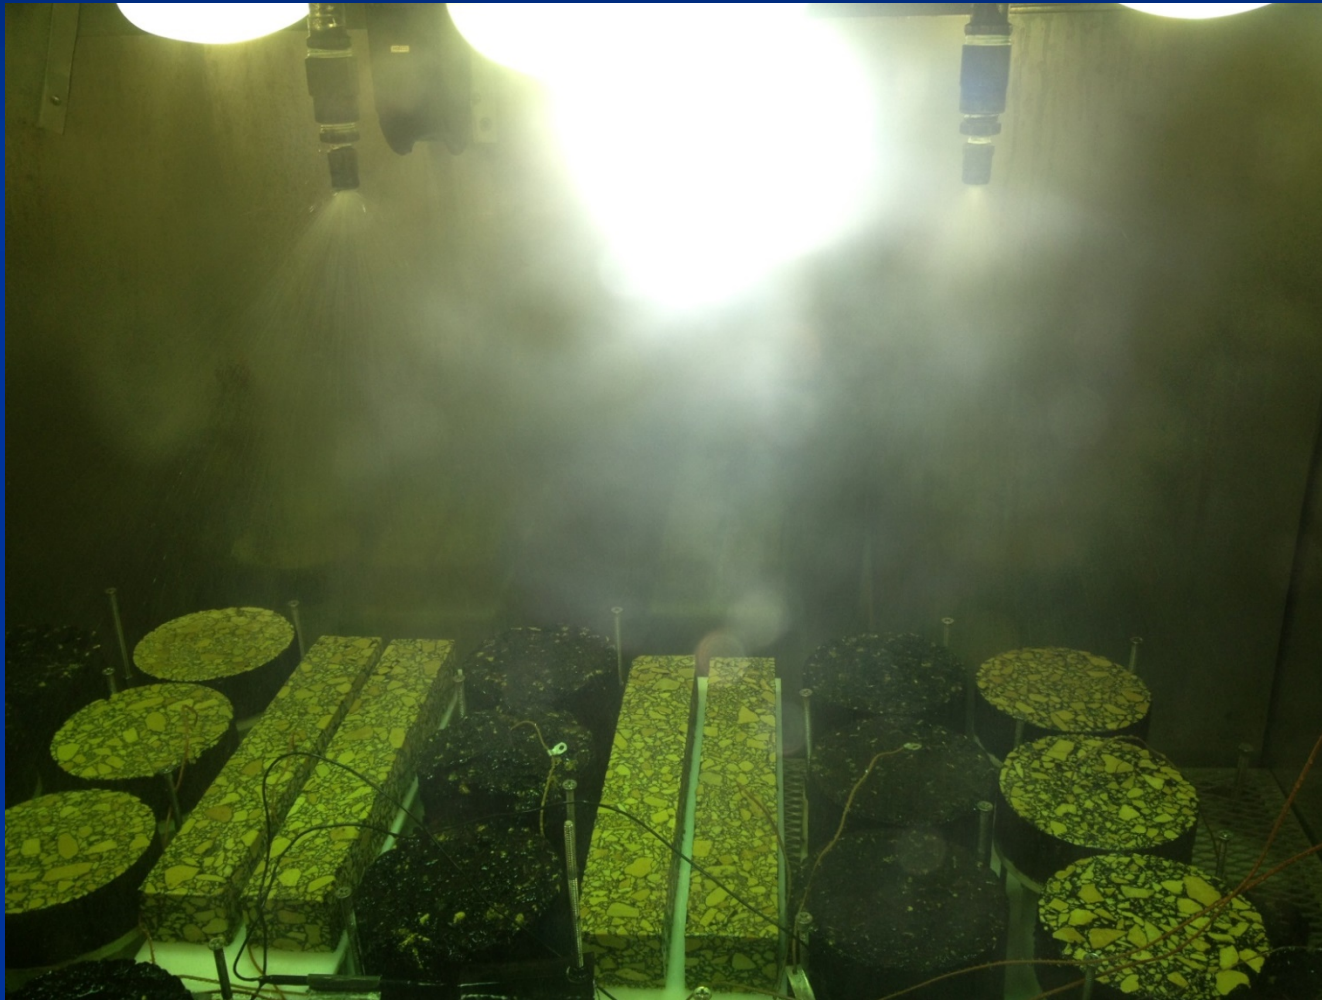

# Aging

- Compare short-term aged to long-term aged performance properties and the asphalt performance grade
- Short-term aged:
  - 2 hours at 135°C prior to compaction
- APWS Aged
  - 3,000 hours total ( $\approx$  15+ years)
  - High Temperature = 60-65°C (simulated pavement surface temperature)
  - Continuous sunlight
  - 1 cycle = 51 minutes dry, 9 minutes wet ('rain')
    - Thermal shock =  $\Delta$  temperature  $\approx$  30-40°F
  - 24 cycles each day

# N70, and N70 + 20% RAP Mix Gradation

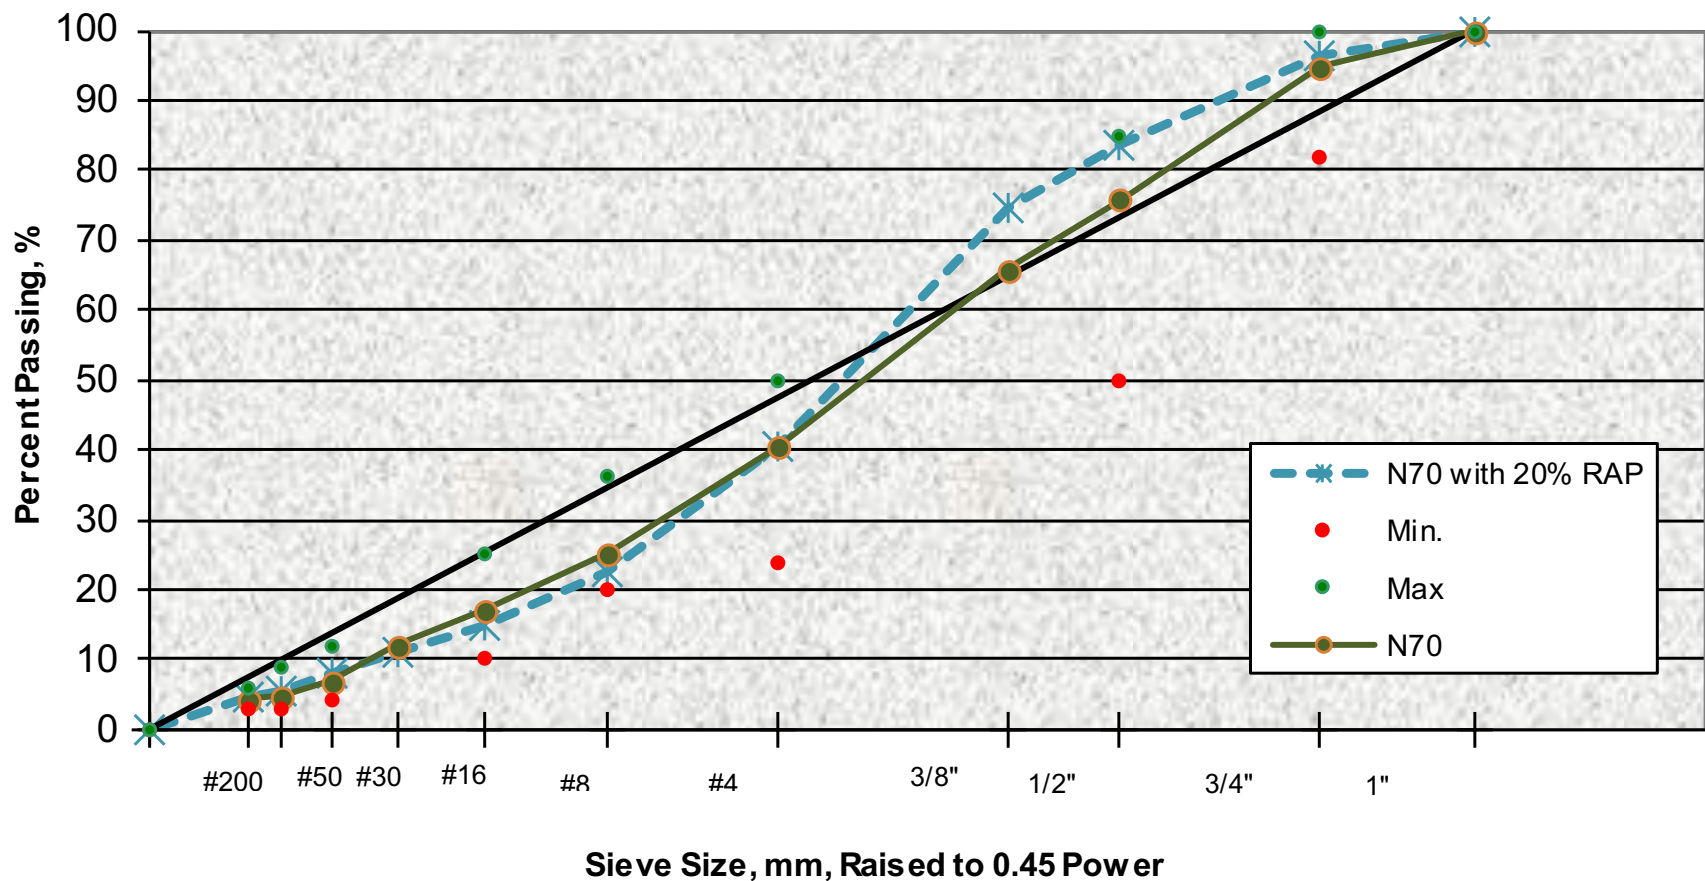




# N70 RAP Mix Properties

N70 with 20% RAP Volumetric Properties					
Parameters	Illinois Standard Specification	Control	2% EcoAddz	6% EcoAddz	10% EcoAddz
Design Gyration	70	70	70	70	70
True PG Grade Recovered	--	69.3-24.8	66.0-26.8	66.3-27.8	66.7-28.2
Percent Binder, Pb(%)	4.0 to 7.0	5.4	5.4	5.4	5.4
Absorbed Asphalt, Pba, %	--	1.2	1.1	1.1	1.1
Effective Asphalt Content, Pbe, %	--	4.2	4.4	4.4	4.4
Air Voids in Compacted Mixture, Va, %	--	4.0	3.6	4.0	4.0
Volume of Voids in Mineral Aggregate, VMA, %	13 minimum	13.8	13.8	14.1	14.1
Dust Proportion, DP, %	1.4 max	1.0	1.0	1.0	1.0


# Blends Continuous Grades

## Original and Recovered

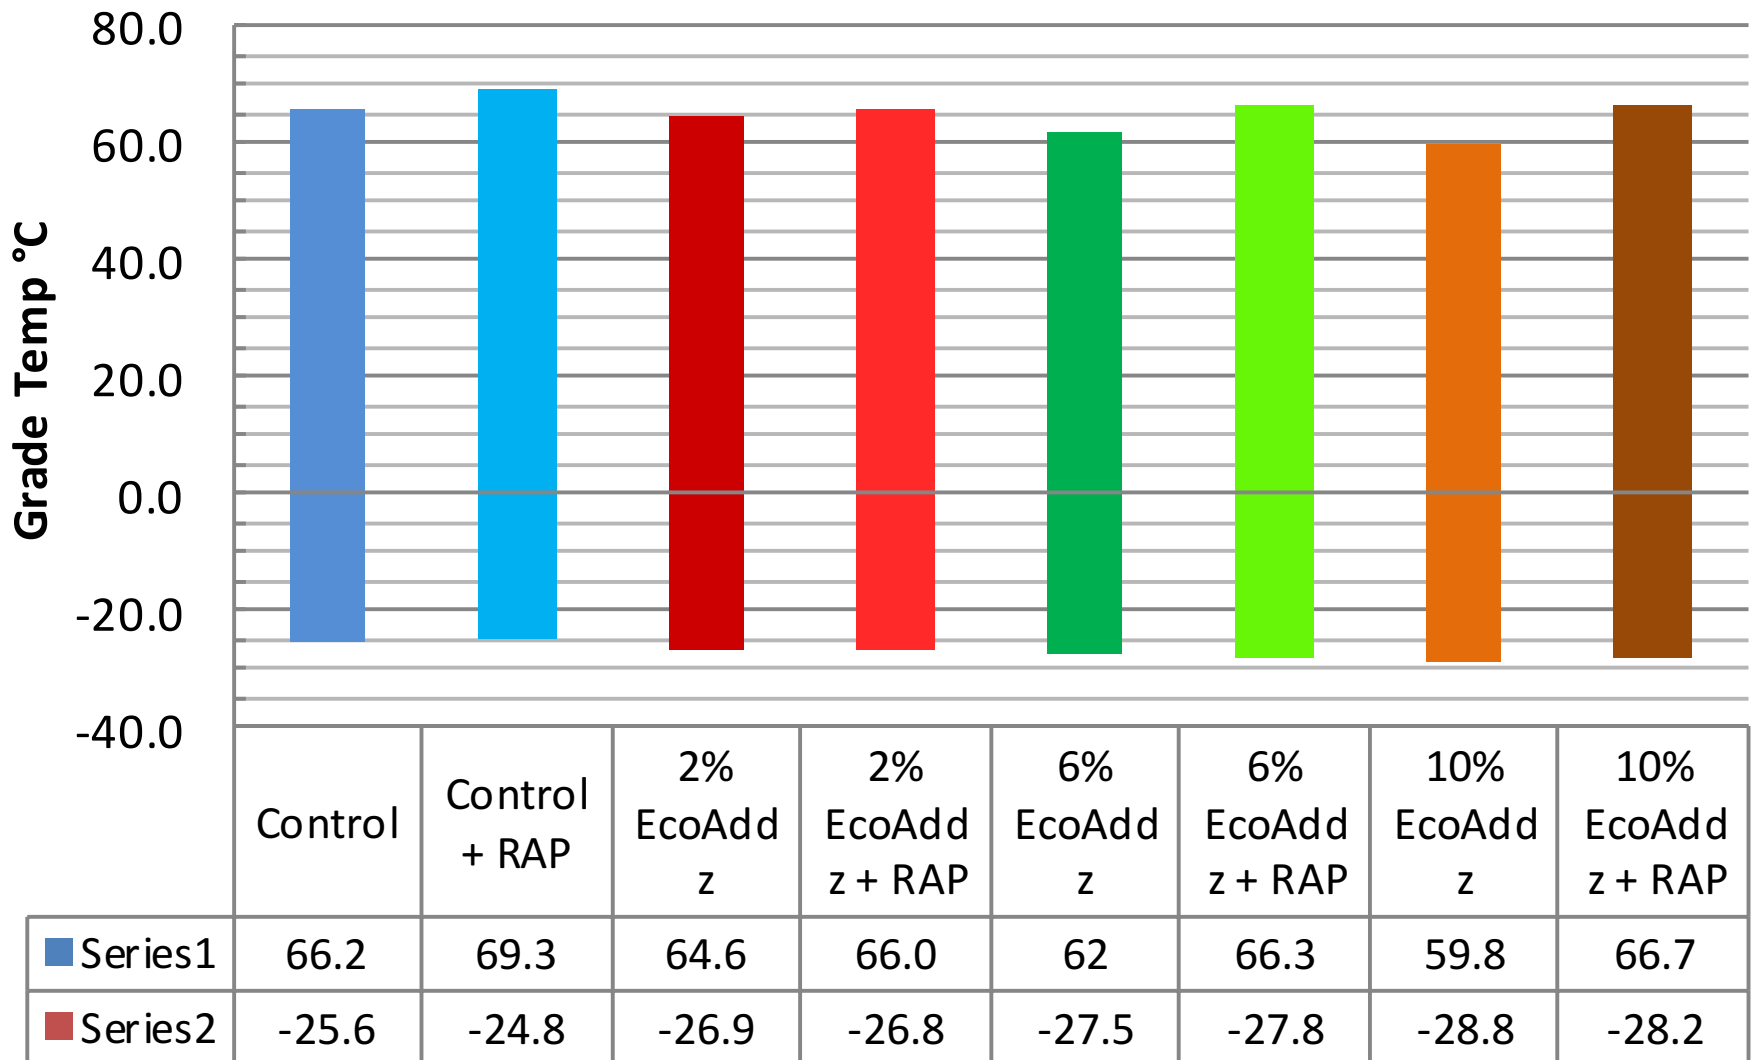

# Recovered Binder after APWS

## N70 RAP Mix

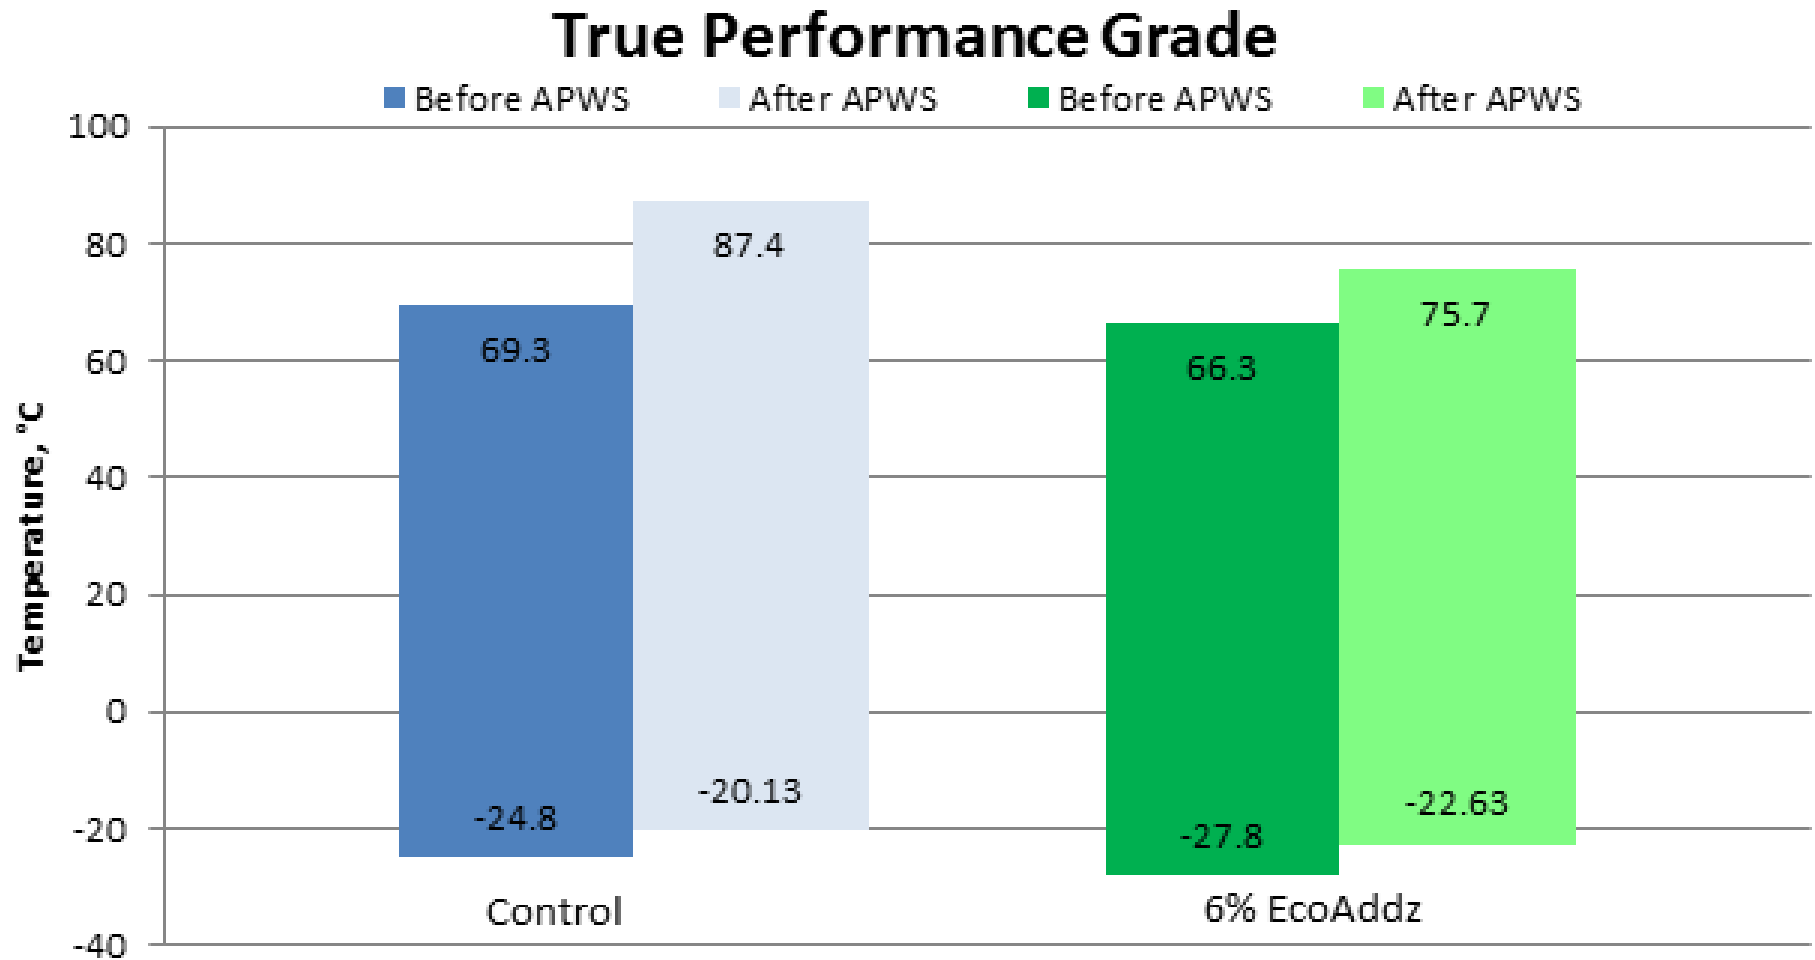


# Recovered Binders


- The addition of 20% RAP only had a minor affect on recovered binder grades.
- EcoAddz modified binders had almost no loss of low temperature properties for the recovered binders.

# VTAE Blend Results

## N70 Hamburg Loaded Wheel Results

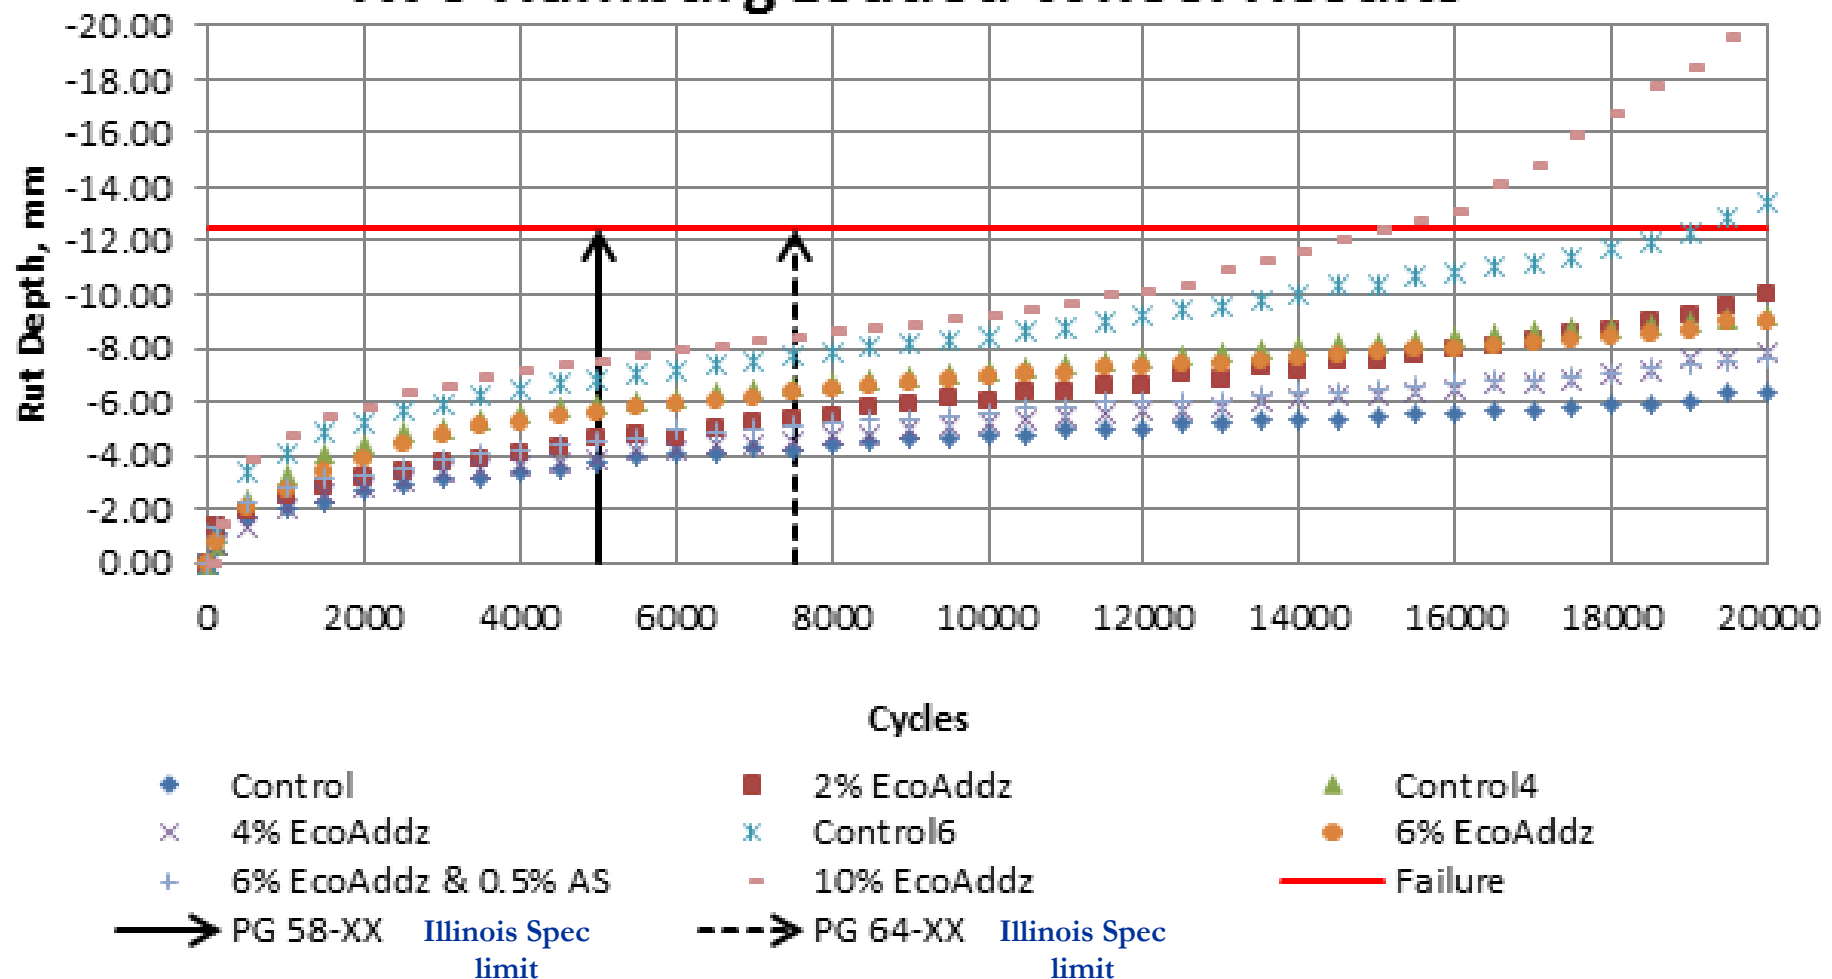


# N70 Mix 20% RAP HWT

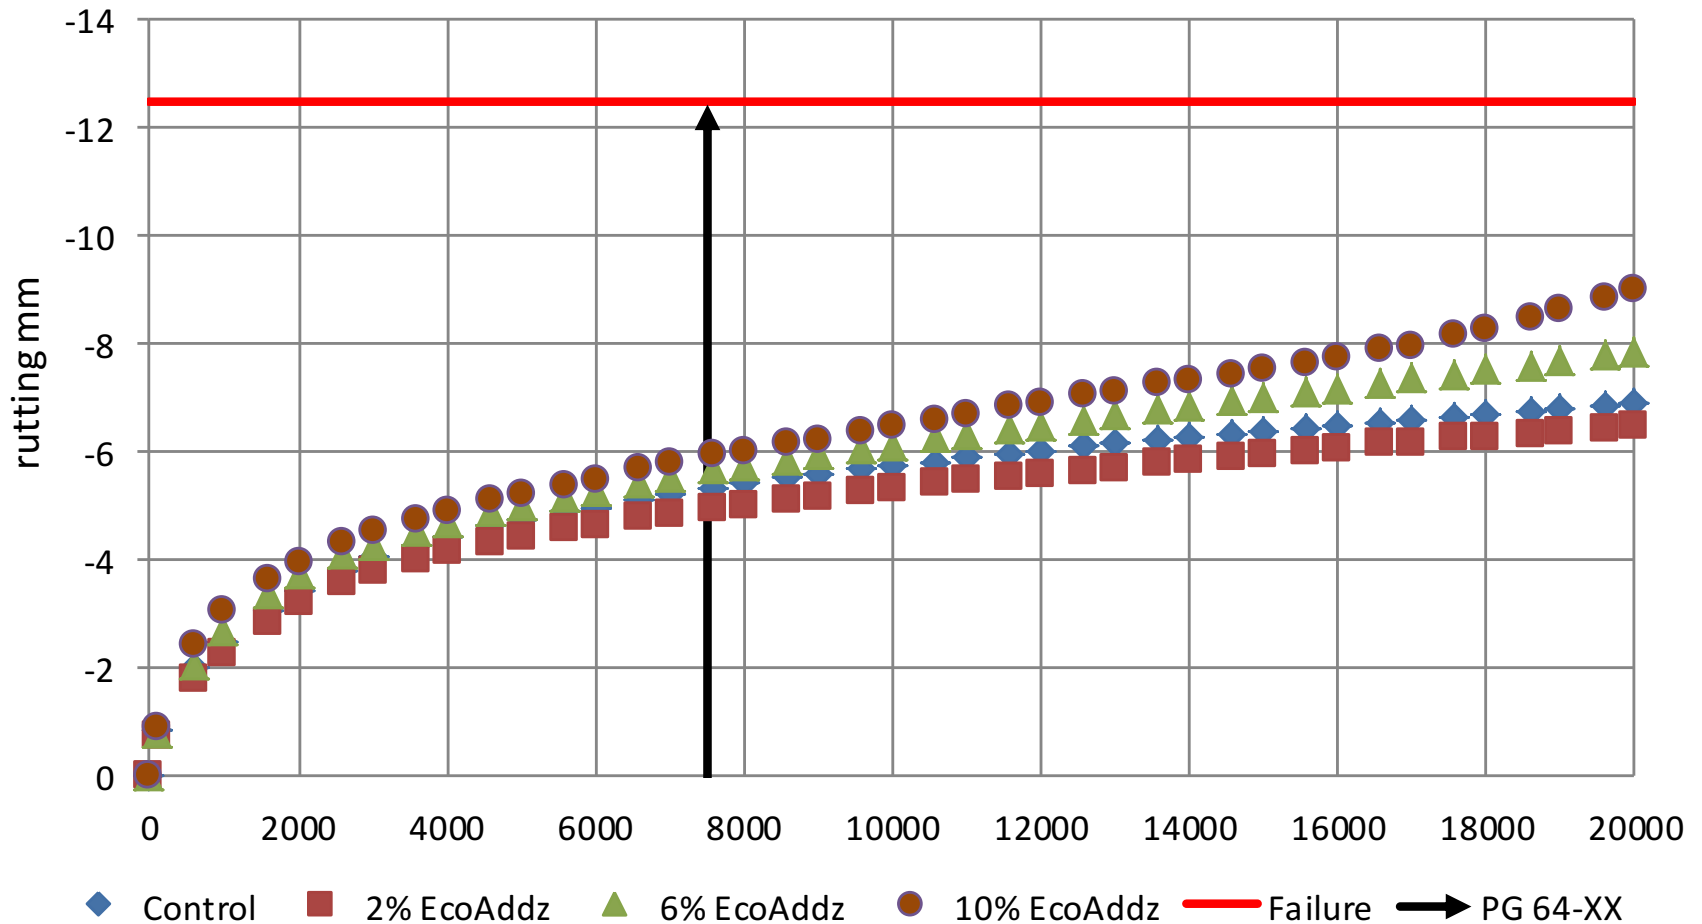




# N70 RAP mixes After APWS

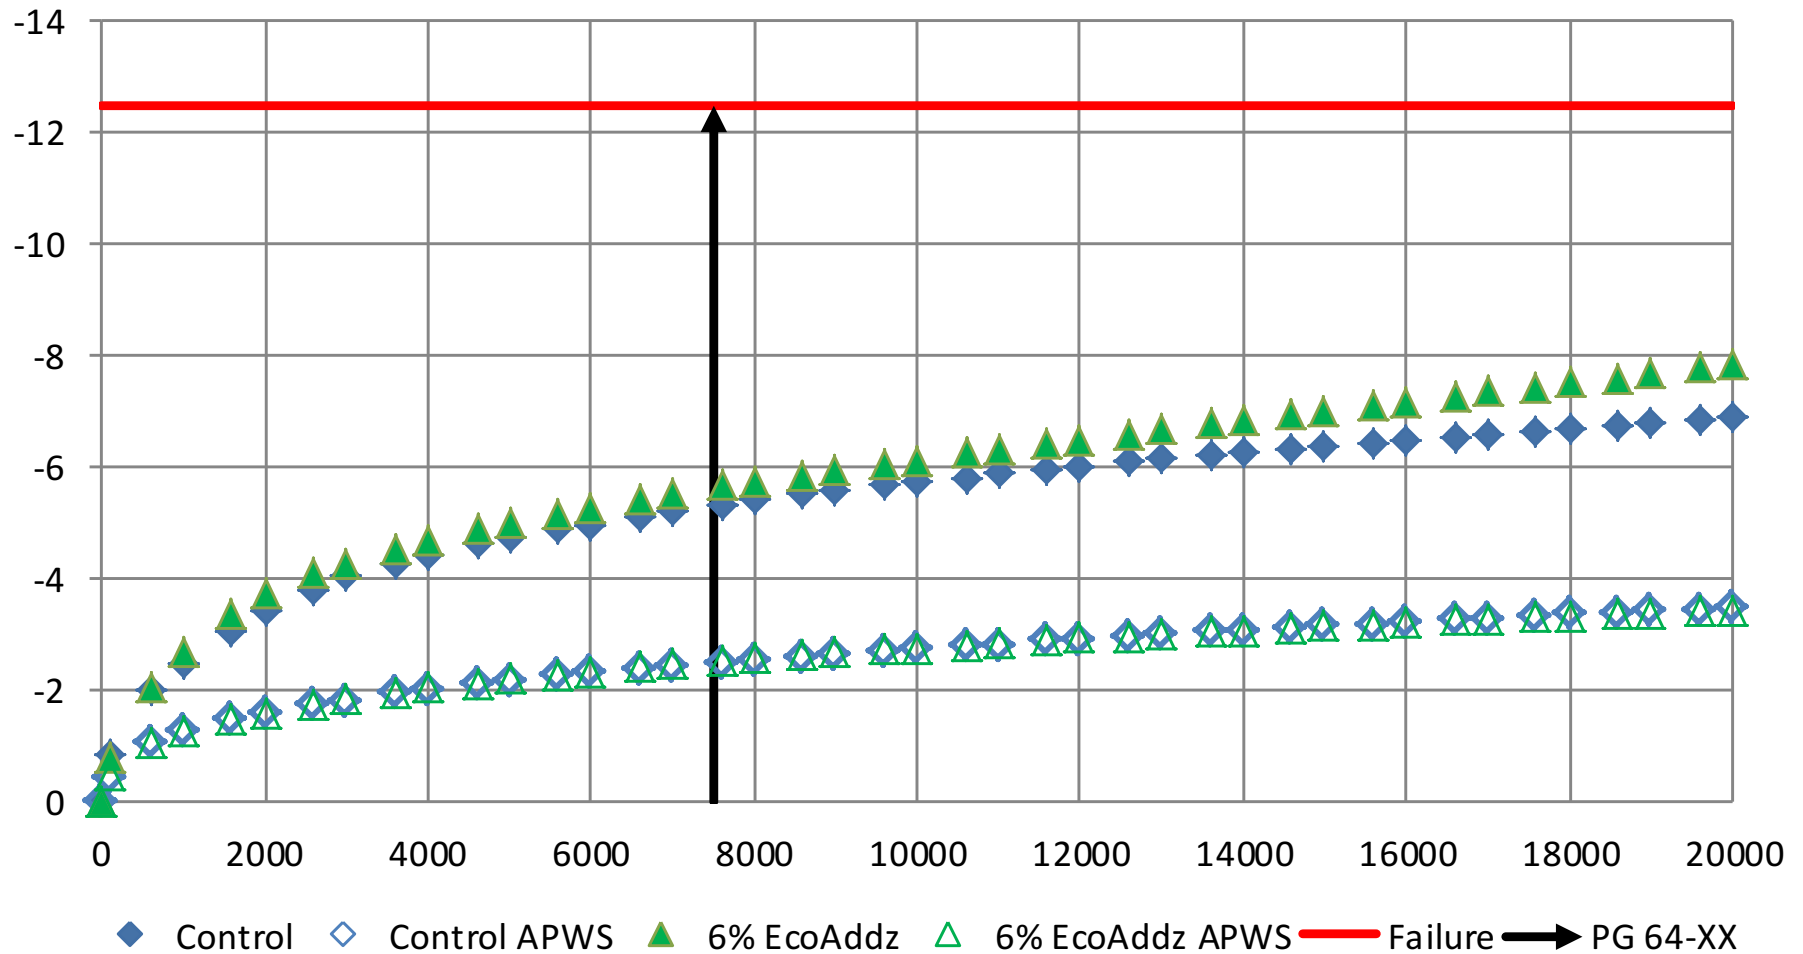


# Hamburg LWT

- The addition of RAP only caused minor increases in stiffness and minor reduction rutting.
- The VTAE mixes did not cause significant reduction of the high temperature properties.
- Long term aging provided similar increased stiffness of control and 6% EcoAddz mixes

# N70 Mix 20% RAP Master Curves 20C

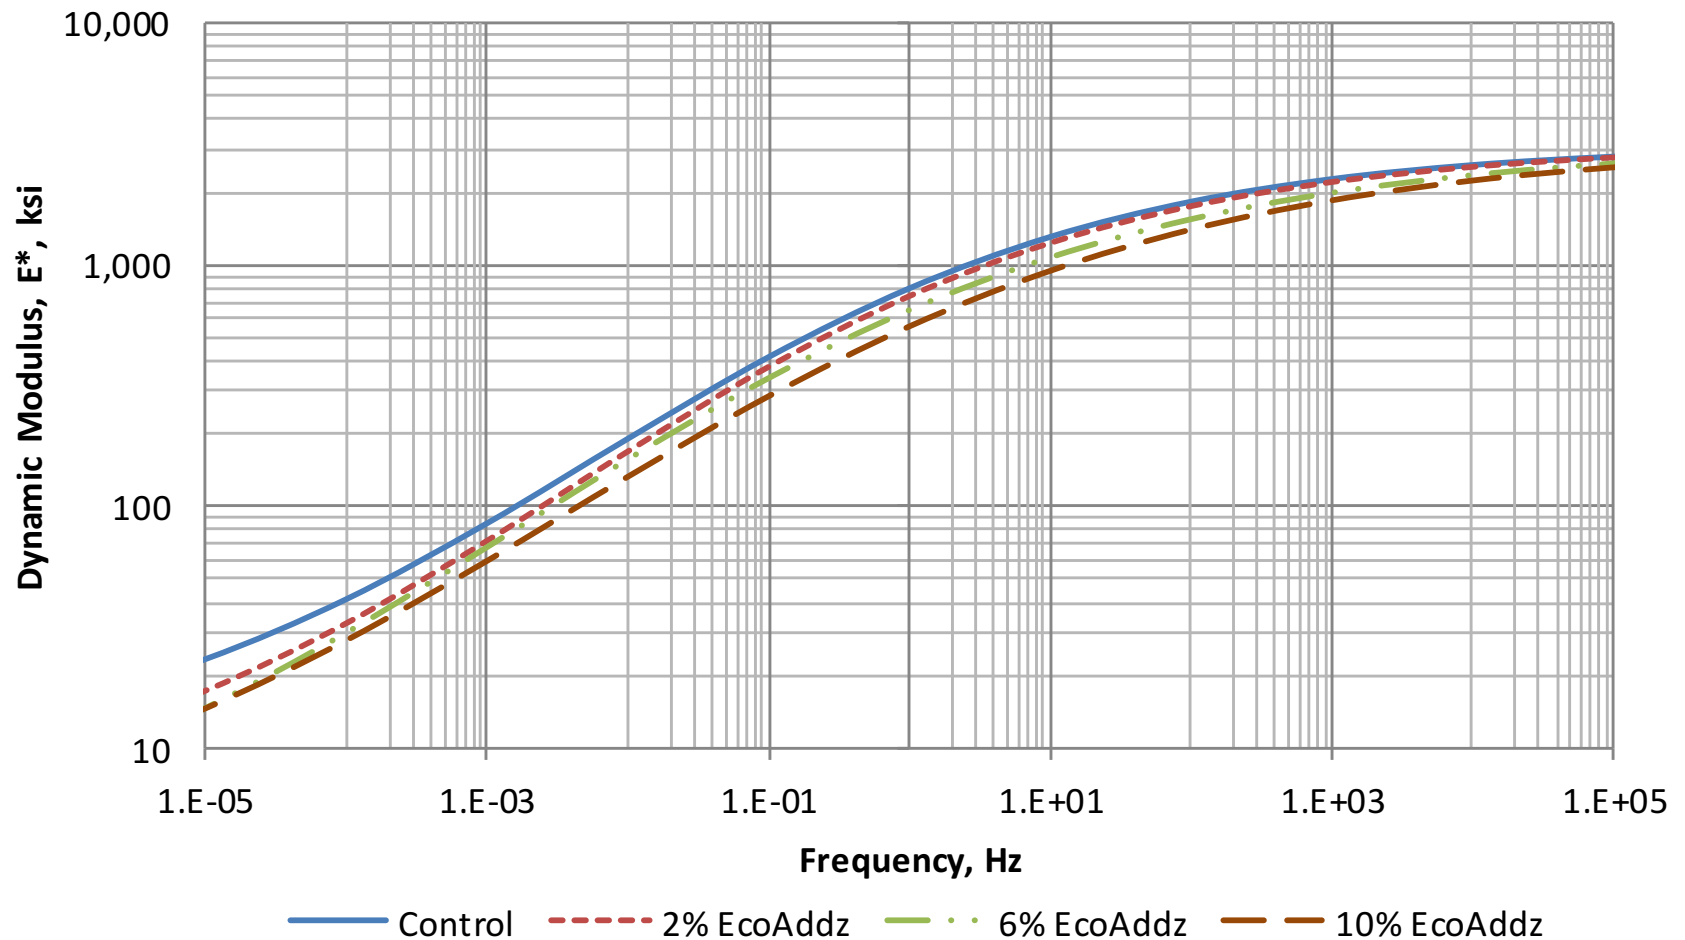


# N70 Mix no RAP Master Curves 20°C

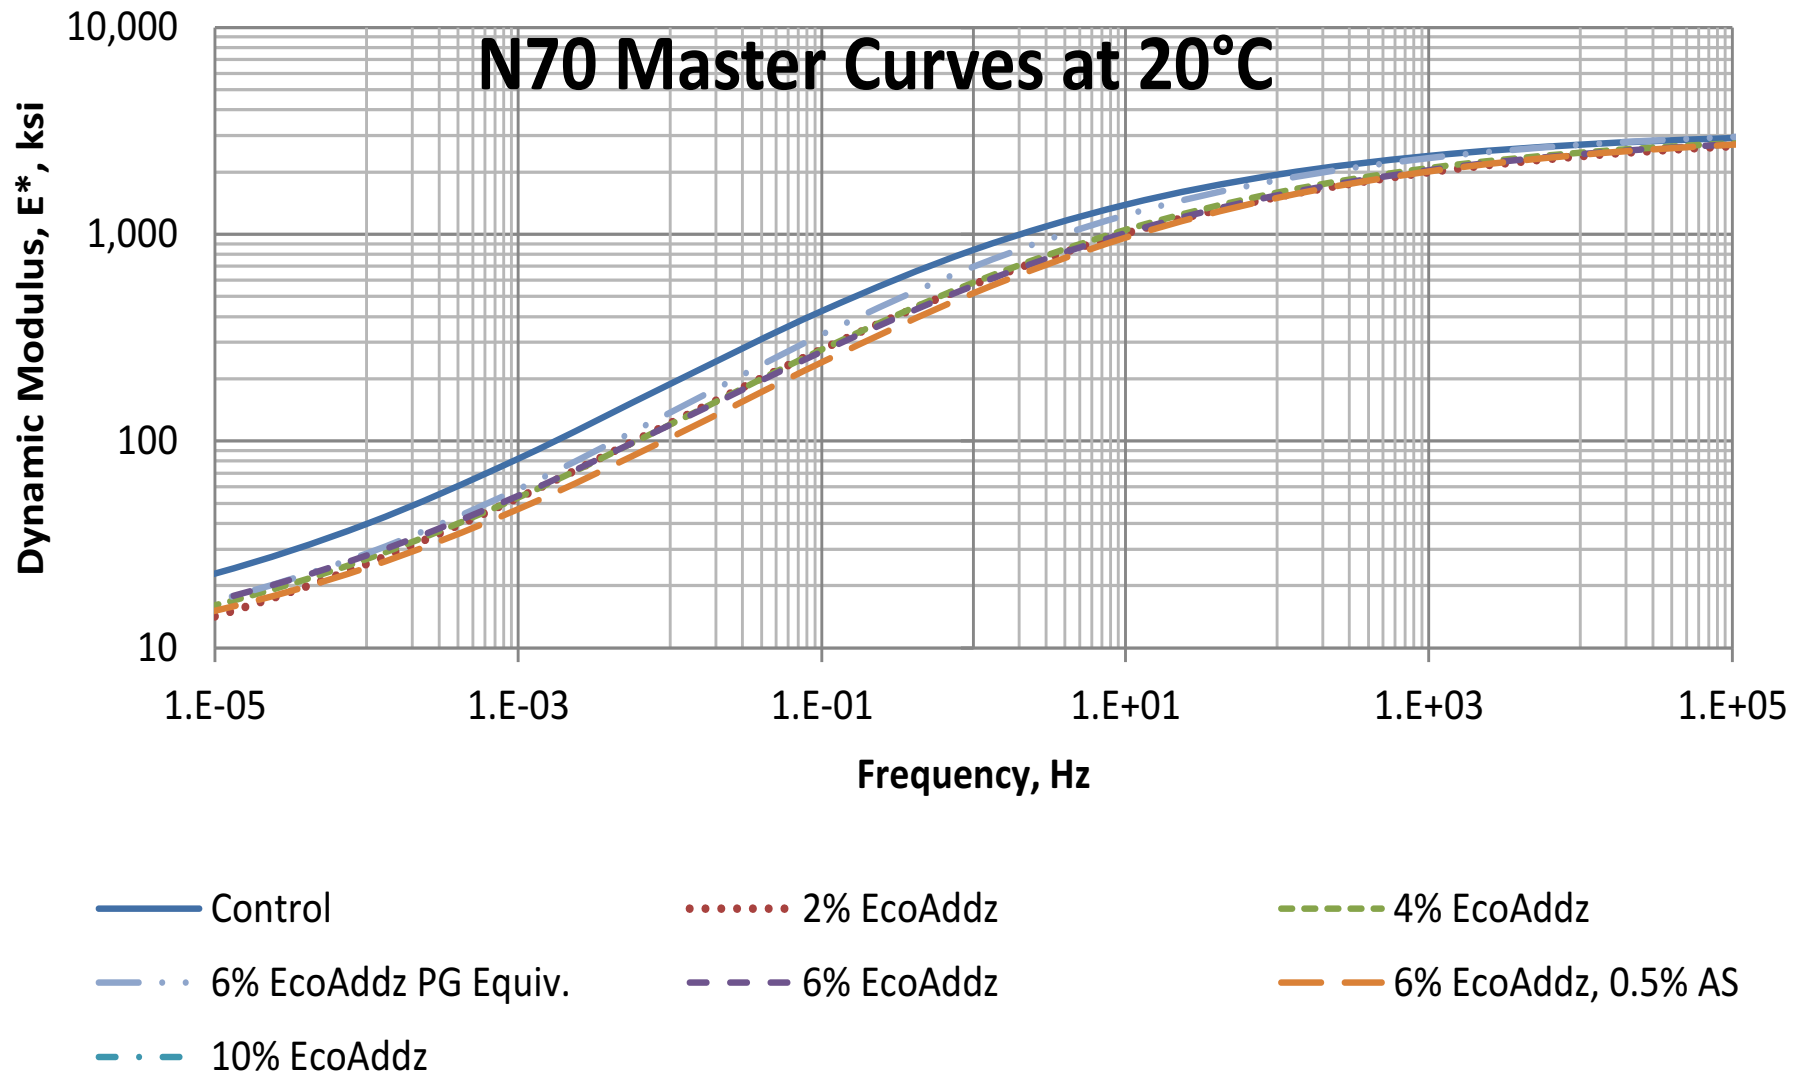

# Master Curves


- The master curve data strictly matches binder PG grade.
- Softer binder lower  $E^*$  data.
- RAP only shows minor increase in mix stiffness.

# N70 Mix 4 Point Bending Beam

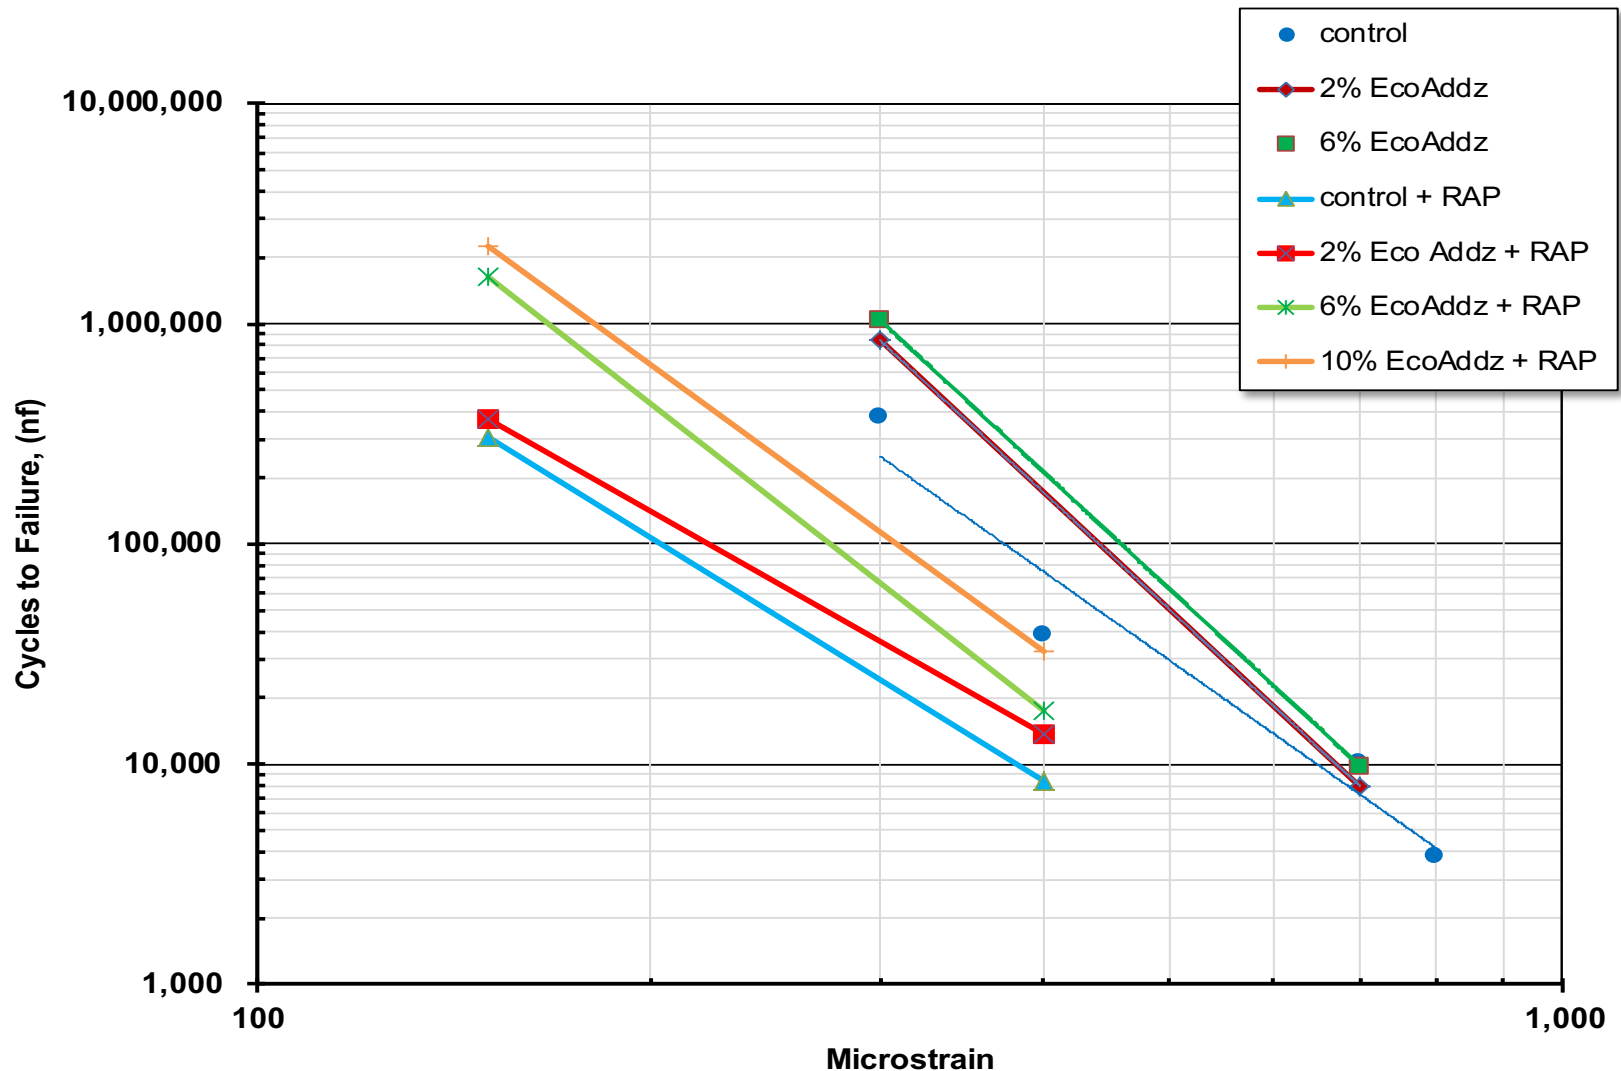




# N70 Mix + RAP 4 Point Bending Beam Before and After APWS

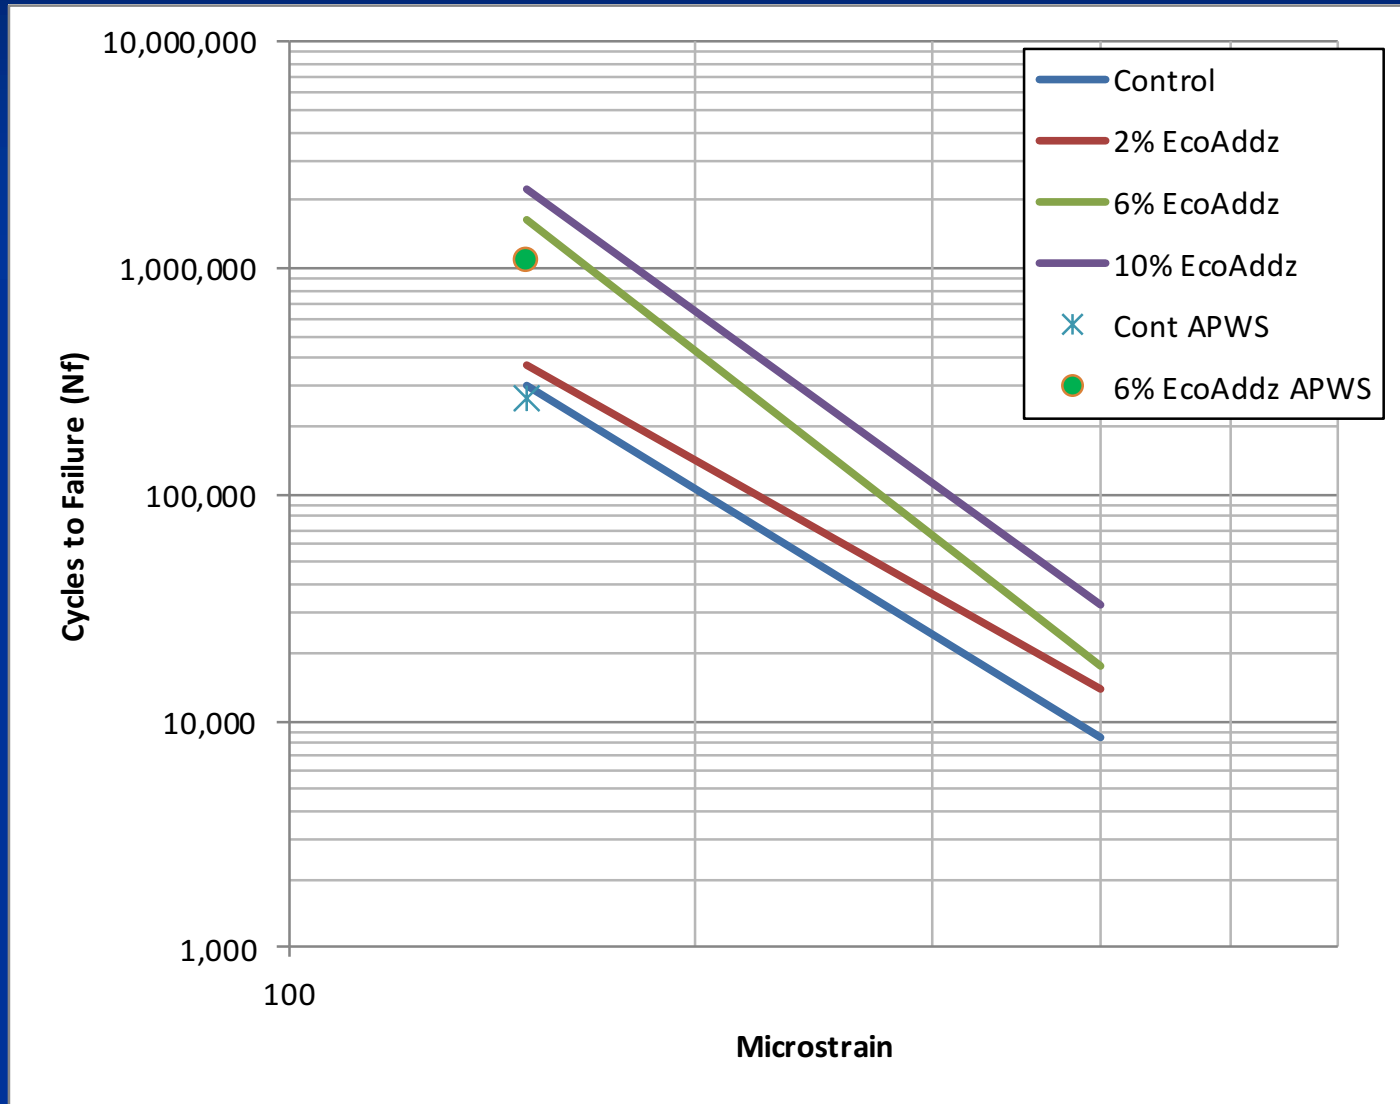

# Beam Fatigue Testing


- The four point bending beam data clearly shows the mixes produced with VTAE have better fatigue response than control binder
- The Addition of RAP Clearly reduces fatigue response. EcoAddz improved Fatigue response of the RAP mix.
- Accelerated aging only showed minor loss in fatigue response.

# DCT Fracture Energy N70 Mix

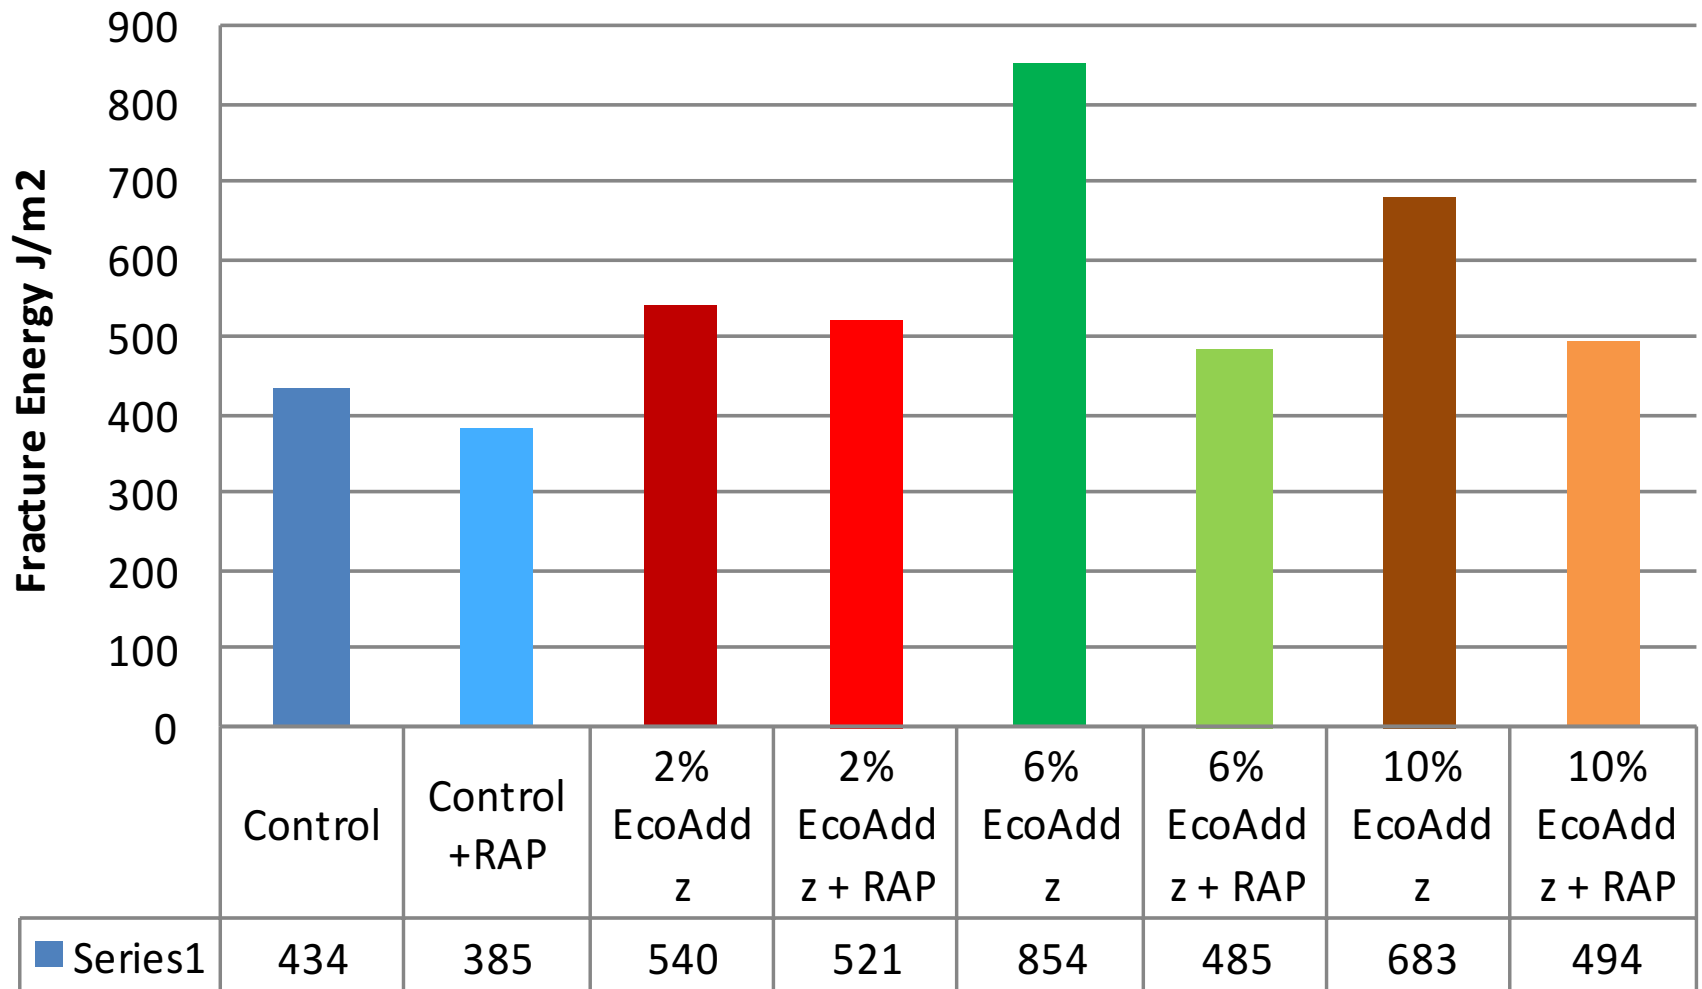


# Results- Fracture Energy; ASTM D 7313

- Fracture Energy tested at  $-12^{\circ}\text{C}$
- MN Research indicates  $400 \text{ J/m}^2$  to be an acceptable minimum Fracture Energy for Unaged Samples

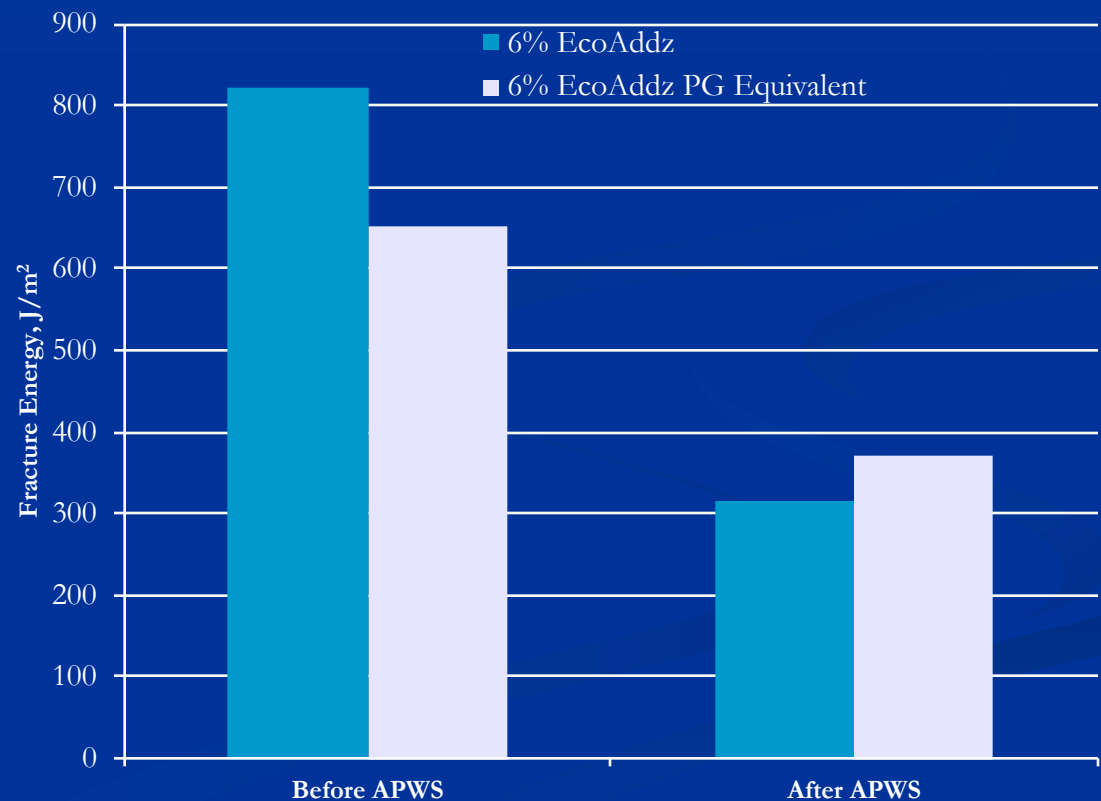

# N70 RAP Mixes Fracture Energy -12 C

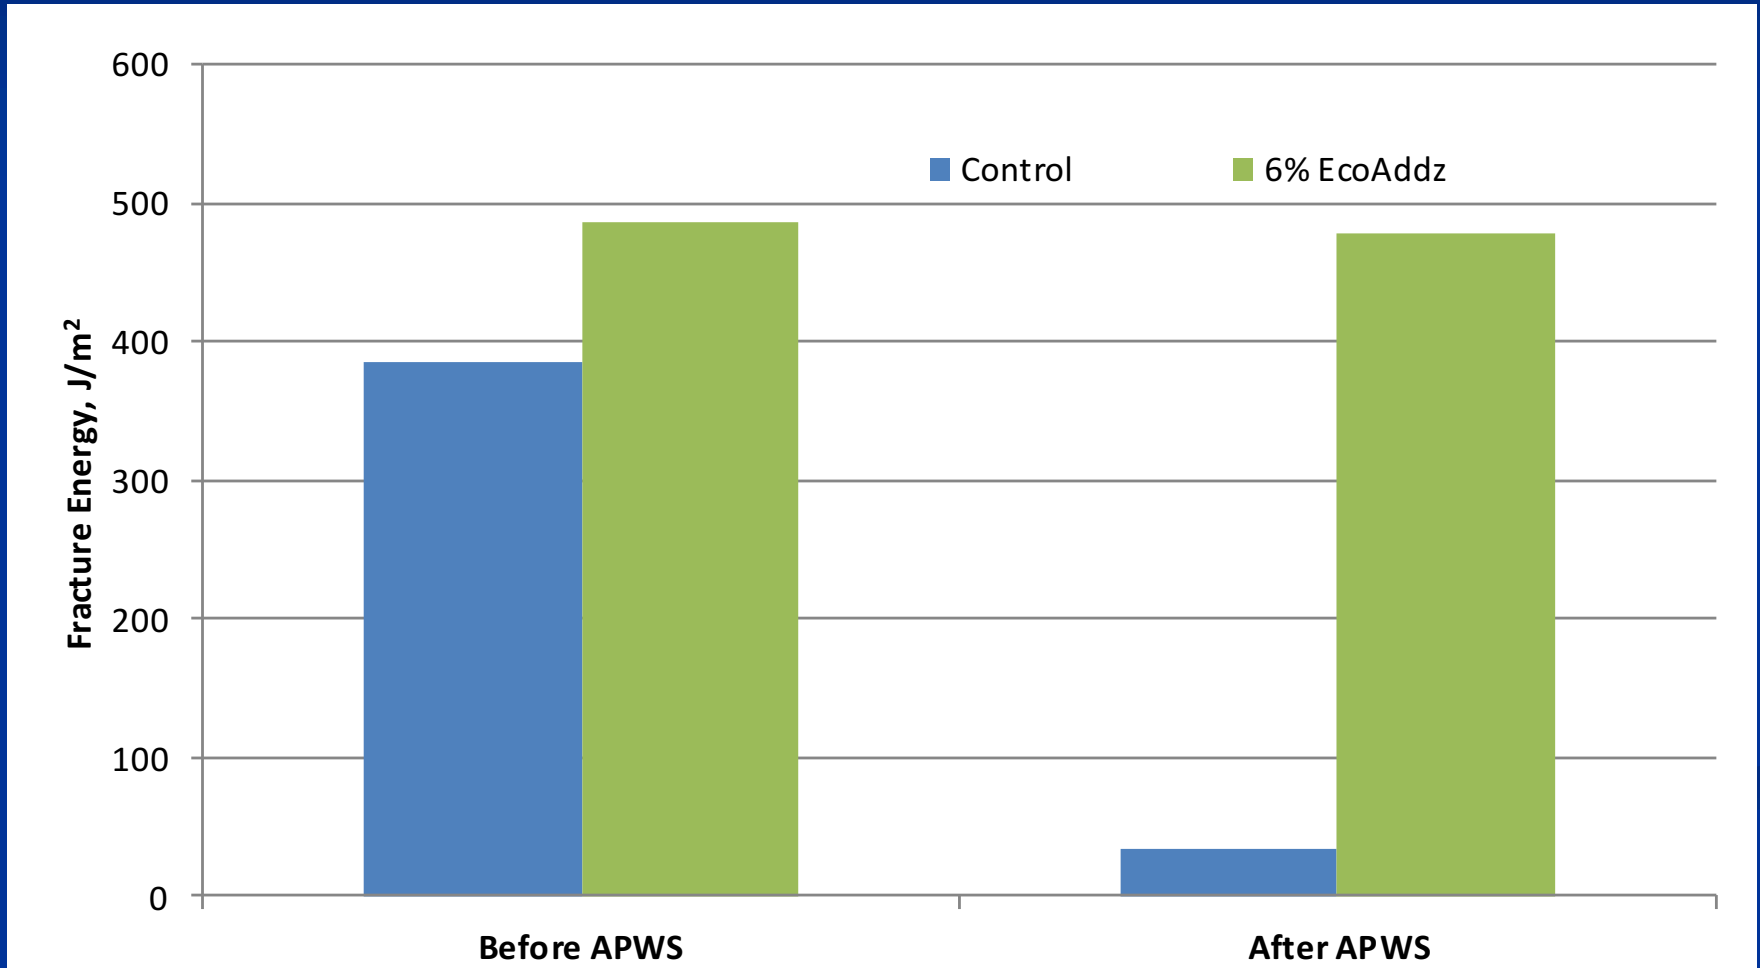

# Fracture Energy Results

- On unaged samples the addition of RAP created a smaller reduction in Fracture Energy on base binder than EcoAddz modified binder.
- On long term aged mix RAP caused significant loss in Fracture Energy of base binder. EcoAddz modified binder indicated only minor loss of fracture energy.



# Summary

- The recovered binder of RAP mixes indicate that the RAP has only minor affect on binder properties. EcoAddz provides minor improvement.
- Mix properties correlate well recovered binder properties on unaged samples.
- Long term aging indicates significant change in properties of mix with RAP.
- EcoAddz modified binder mitigated some of the long term aging effects.

Thank you

Questions